


Solid-State Lighting: *An Opportunity for Nanotechnologists to Address the Energy Challenge*

Tim Sands
Schools of Materials Engineering and Electrical and Computer
Engineering
Birck Nanotechnology Center

Outline

- ◆ The terawatt challenge
- ◆ Solid-state lighting - *the opportunity*
- ◆ Lighting - *a brief history*
- ◆ Lighting - *a tutorial*
- ◆ Light-emitting diodes
- ◆ Today's LED lighting technologies
- ◆ Challenges to meeting the SSL goal
- ◆ Potential nanotech solutions

The terawatt challenge

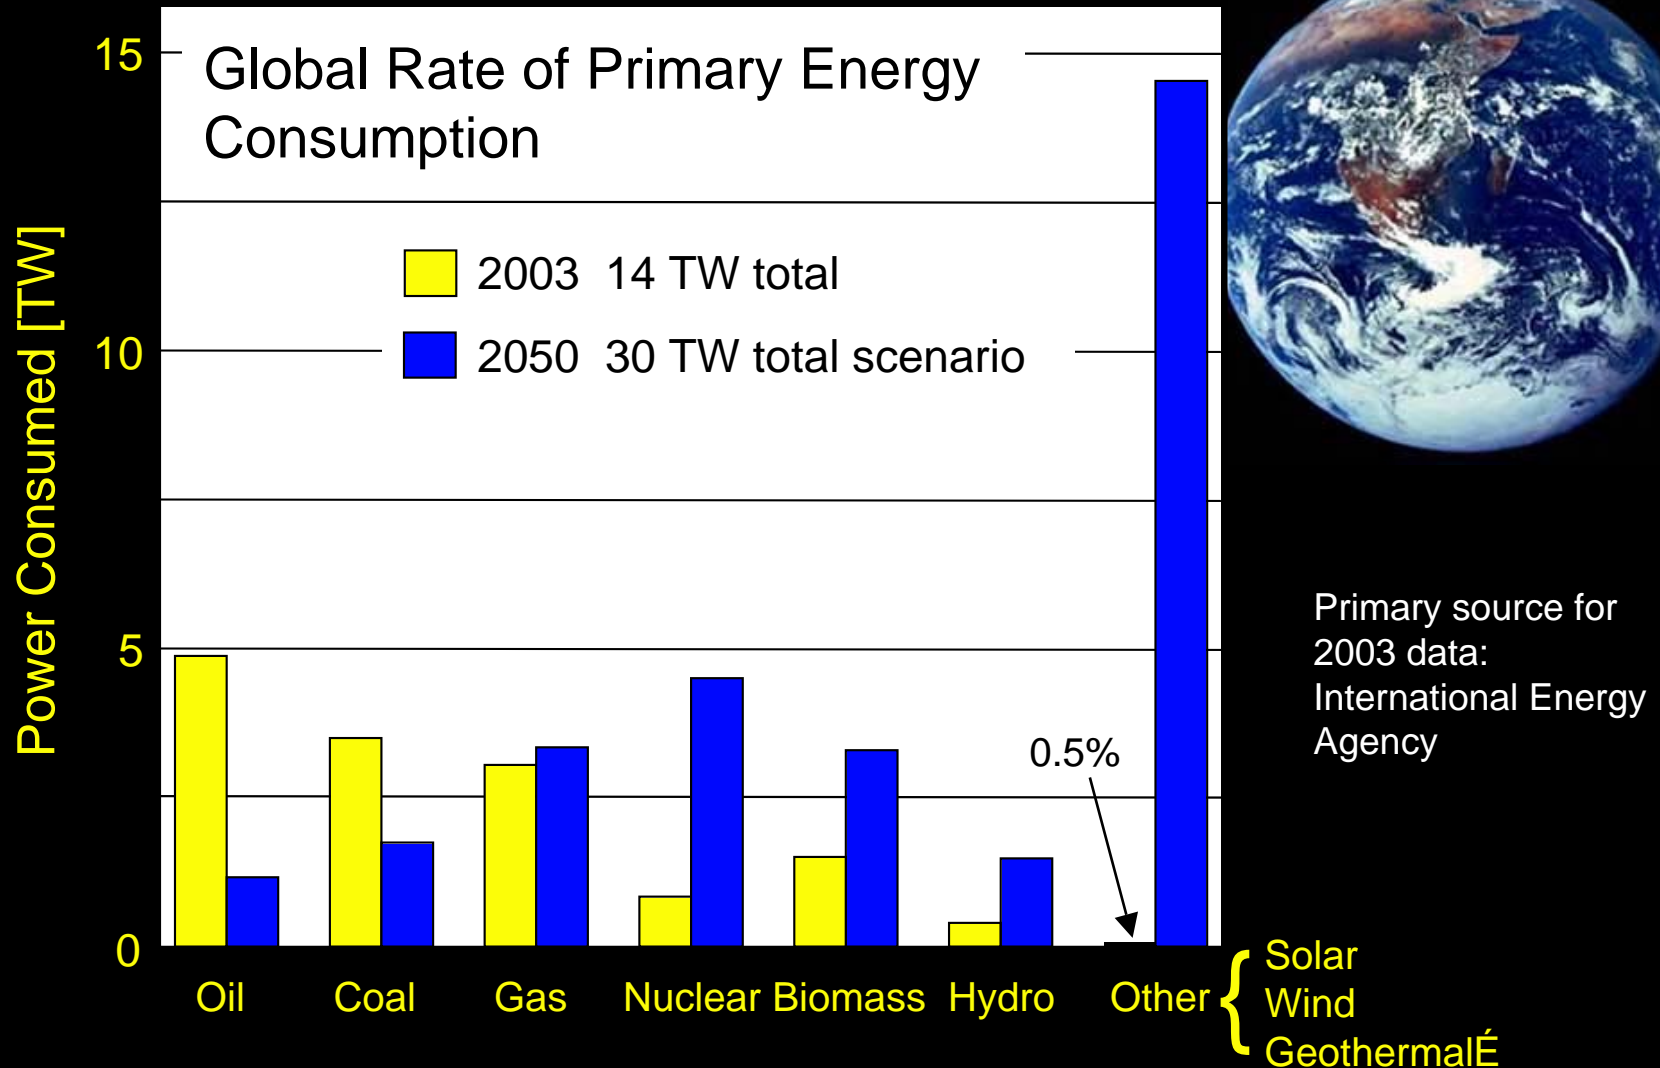

Adapted from Richard Smalley's presentation on "Our Energy Challenge" at the 2004 International Electron Devices Meeting (IEDM), San Francisco, CA 12/14/04

Energy consumption rate *per capita*

◆ In 2003:

- ◆ World: 2.24 kW/person (6.268 B people)
- ◆ US: 10.4 kW/person (0.291 B people)
- ◆ If everyone consumed at the US rate, the global rate of primary energy consumption would be **65 TW**.

◆ In 2050:

- ◆ The projection of 30 TW in 2050 corresponds to an average of 3 kW/person for 10B people...very conservative in light of the rapid changes in the developing world.

Rolling final report

By 2050, it is likely that....

- ◆ The population will grow from 6.5 B to 10 B
- ◆ The rate of global energy consumption will double
- ◆ CO₂ emissions will need to be reduced by a factor of two
- ◆ Oil production will decrease
- ◆ The use of nuclear energy will increase
- ◆ Solar, wind, and geothermal will increase dramatically
- ◆ **Conservation** will be an essential element of the solution

The solid-state part of the solution...

- ◆ More efficient devices for...
 - ◆ LED-based lighting
 - ◆ Thermoelectric refrigeration
 - ◆ Thermoelectric and thermophotovoltaic conversion of waste heat
 - ◆ Photovoltaic conversion of solar energy and production of hydrogen
- ◆ Added benefits
 - ◆ Compact
 - ◆ Robust
 - ◆ Low environmental impact
- ◆ Challenges
 - ◆ Efficiency breakthroughs needed!
 - ◆ Availability and price of raw materials
 - ◆ Manufacturing costs

The ^{nano} solid-state part of the solution...

- ◆ More efficient devices for...
 - ◆ LED-based lighting
 - ◆ Thermoelectric refrigeration
 - ◆ Thermoelectric and thermophotovoltaic conversion of waste heat
 - ◆ Photovoltaic conversion of solar energy and production of hydrogen
- ◆ Added benefits
 - ◆ Compact
 - ◆ Robust
 - ◆ Low environmental impact
- ◆ Challenges
 - ◆ Efficiency breakthroughs needed! *Nanostructured semiconductors?*
 - ◆ Availability and price of raw materials *Thin films instead of bulk?*
 - ◆ Manufacturing costs *“Bottom-up” nanofabrication?*


Solid-state lighting - *the opportunity*

- ◆ Electricity generation accounts for about 37% of primary energy consumption in the U.S.*
- ◆ Lighting accounts for 22% of the nation's electric power usage.
- ◆ **The DoE Goal:** a solid-state lamp that is more efficient, longer lasting and cost competitive compared to conventional technologies, targeting a system efficiency of 50% and the color quality of sunlight.
- ◆ **Implications of Success:** 33% reduction in energy consumed for lighting by 2025, eliminating need for 41 1000MW power plants, and saving consumers \$128 B+.

Lighting - *a brief history*

- ◆ 1879 - first incandescent lamps by Joseph Swan and Thomas Edison
- ◆ 1901 - first low-pressure mercury vapor discharge lamp by Peter Cooper Hewitt (precursor of modern fluorescent lamps)
- ◆ 1932 - first commercial high-pressure mercury vapor lamp, a “high-intensity discharge lamp” (HID)
- ◆ 1961 - first patent for a metal-halide lamp (Gilbert Reiling)
- ◆ 1965 - first high-pressure sodium lamp
- ◆ 1996 - first commercial white LED (blue + phosphor)

Lighting - *a tutorial*

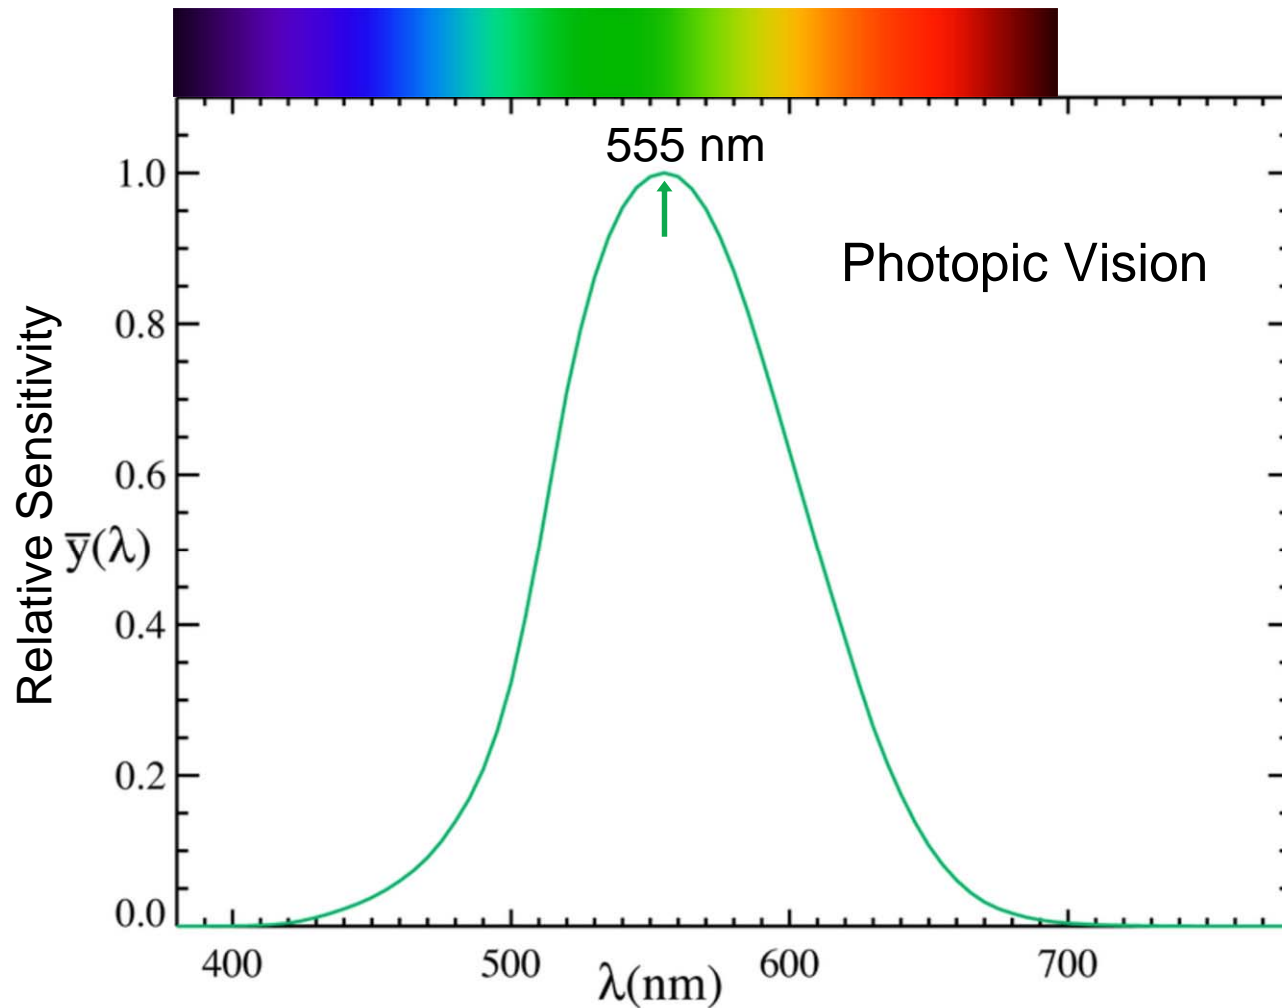


Definitions

- ◆ **Luminous Efficacy:** measure of ability of radiation to produce a visible sensation = luminous flux/radiant flux [lumen/W_{radiant}]
 - ◆ Radiant flux of 1W at $\lambda = 555$ nm produces luminous flux of 683 lumens
 - ◆ Any shift in λ or broadening of spectrum will reduce the luminous efficacy
- ◆ **Luminous Efficiency:** ability of source to convert consumed power into actuation of vision [lumen/W_{elec}] = (radiant flux/consumed power) · luminous efficacy

Color matching


- ◆ **Color Matching Functions:** construct spectrum of source by weighted sums of CMFs to arrive at **Chromaticity Coordinates (x,y)**

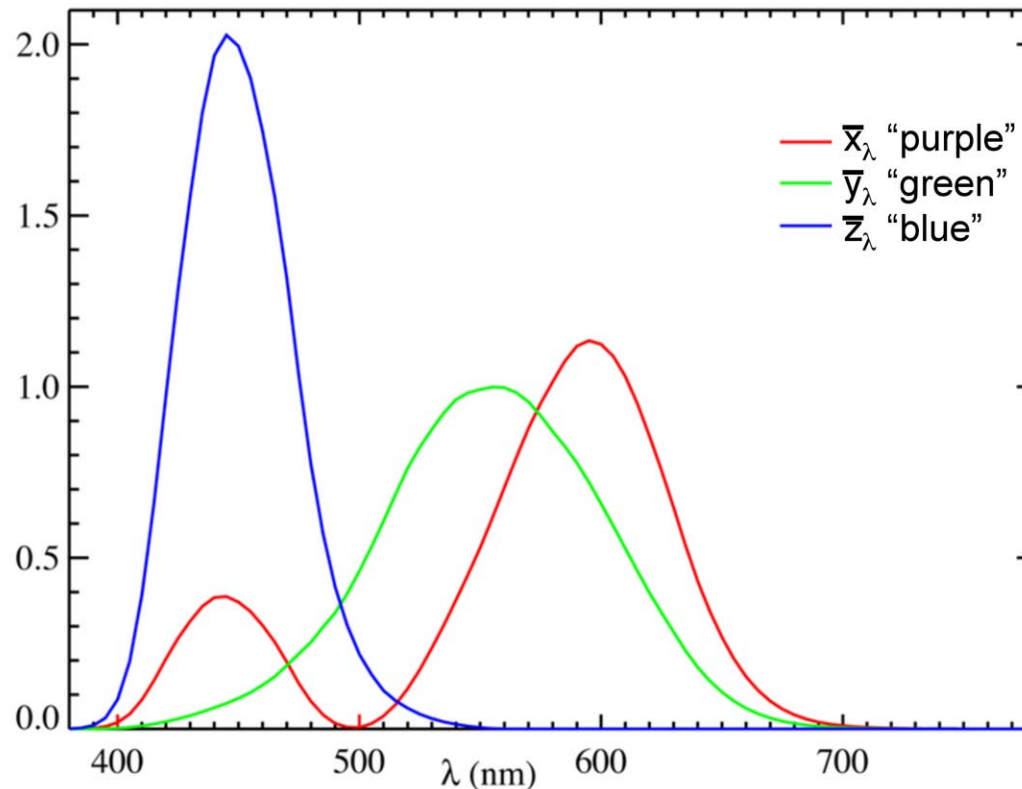

Chromaticity diagram

- ◆ Plot chromaticity coordinates (x,y) of source to yield perceived color
- ◆ Pure (monochromatic) colors on the perimeter


International Commission on Illumination
- abbreviated as CIE from its French title
Commission Internationale de l'Eclairage

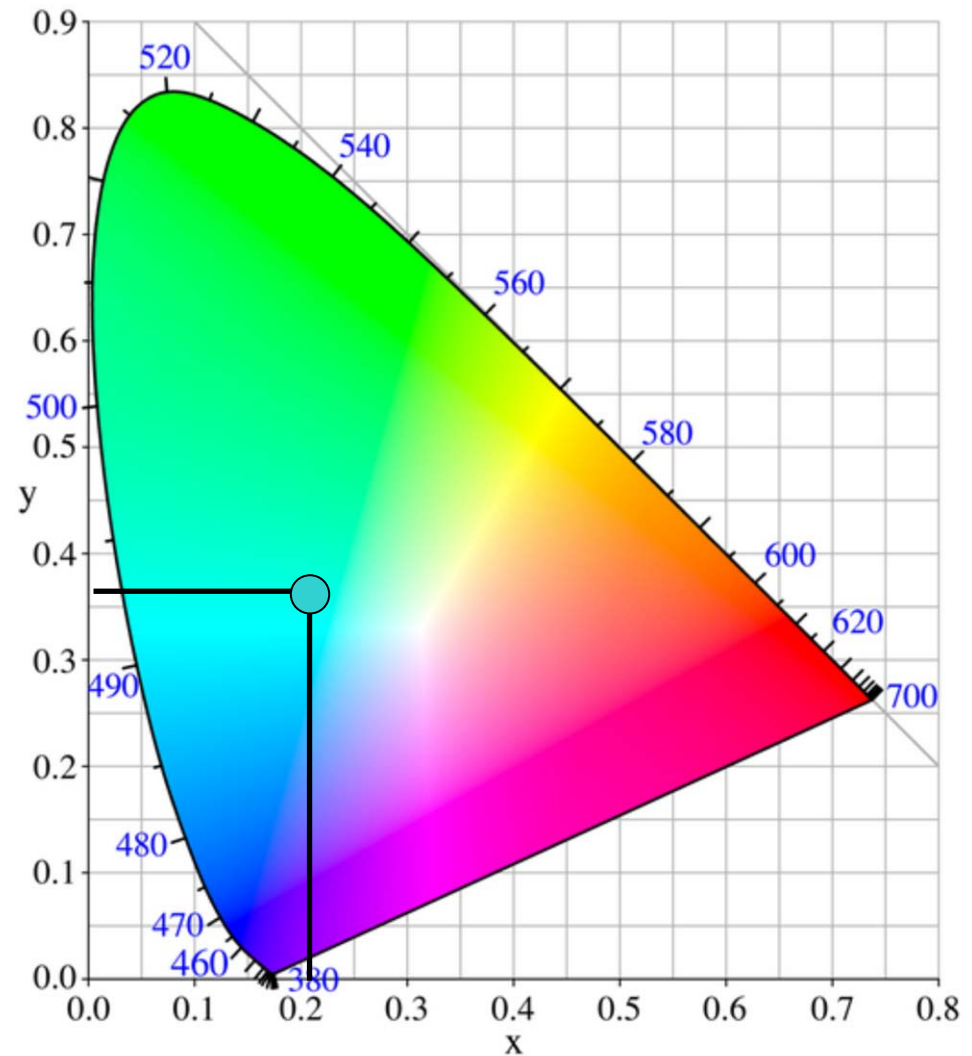

Planckian Locus


- ◆ **Planckian Locus** describes black body color temperature [K].

International Commission on Illumination
- abbreviated as CIE from its French title
Commission Internationale de l'Eclairage

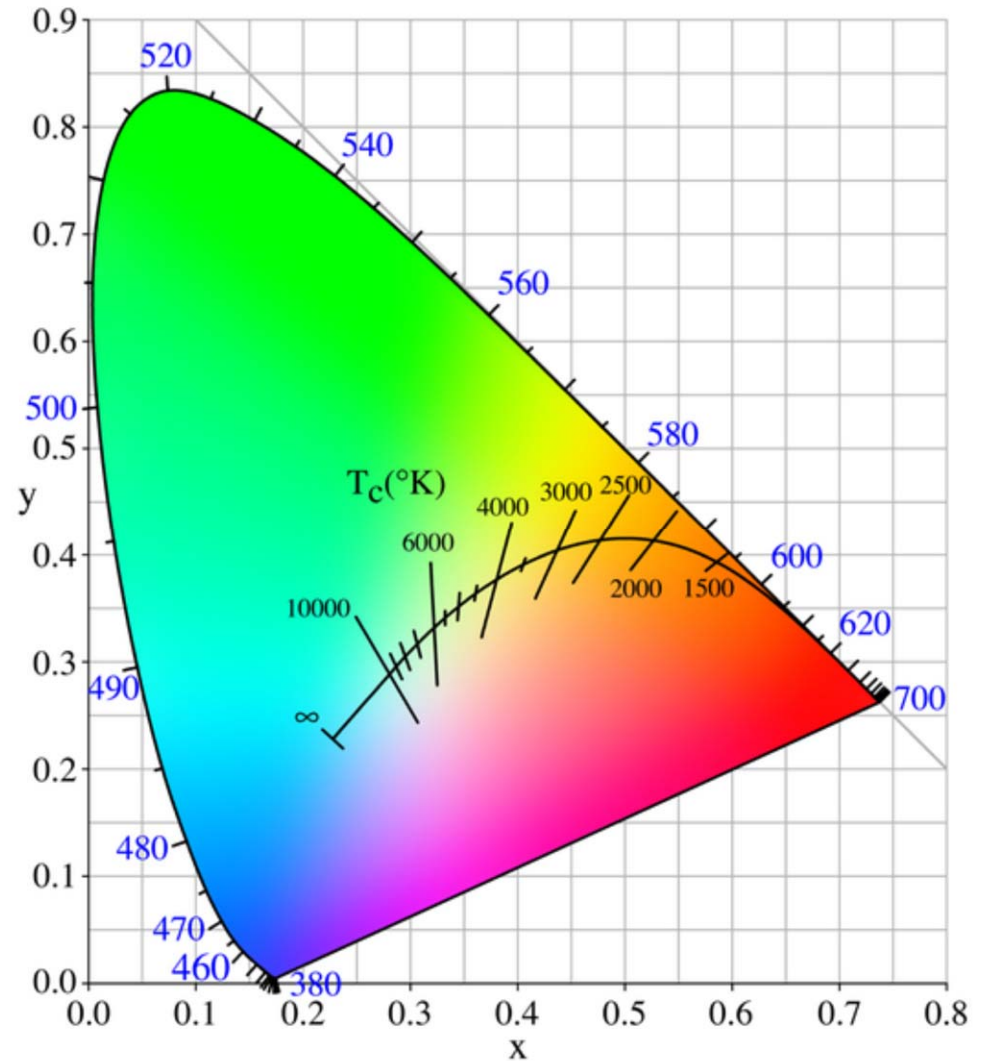


Standard Sources

- ◆ A: Tungsten at 2856K
- ◆ B: Direct sunlight - 4870K
- ◆ C: Overcast sunlight - 6770K
- ◆ D_{65} : Daylight - 6504K
- ◆ E: Point of equal energy $(x,y) = (0.33,0.33)$

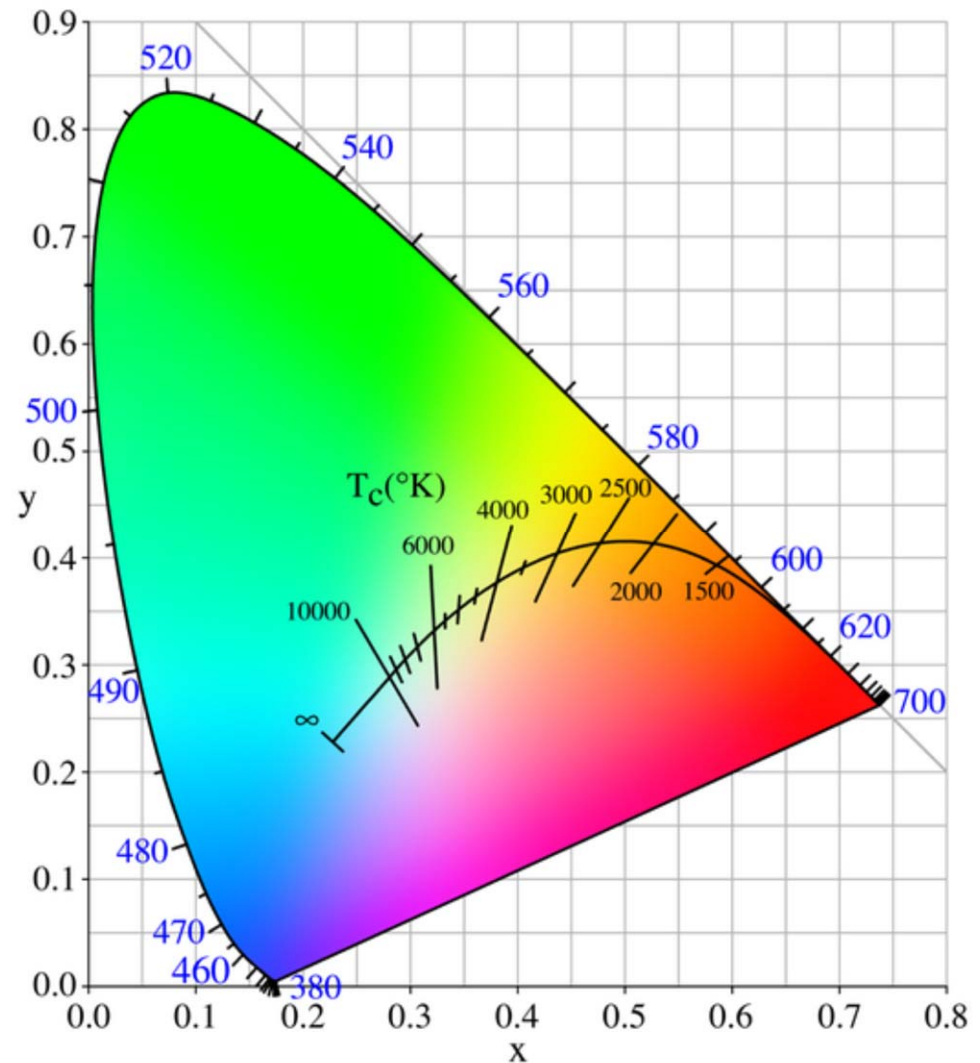


Color Rendering

- ◆ A blue + yellow source, properly weighted, is perceived as white, but will not satisfactorily render color upon reflection
- ◆ The color quality is defined by the **Color Rendering Index (CRI)**, defined as 100 for sunlight

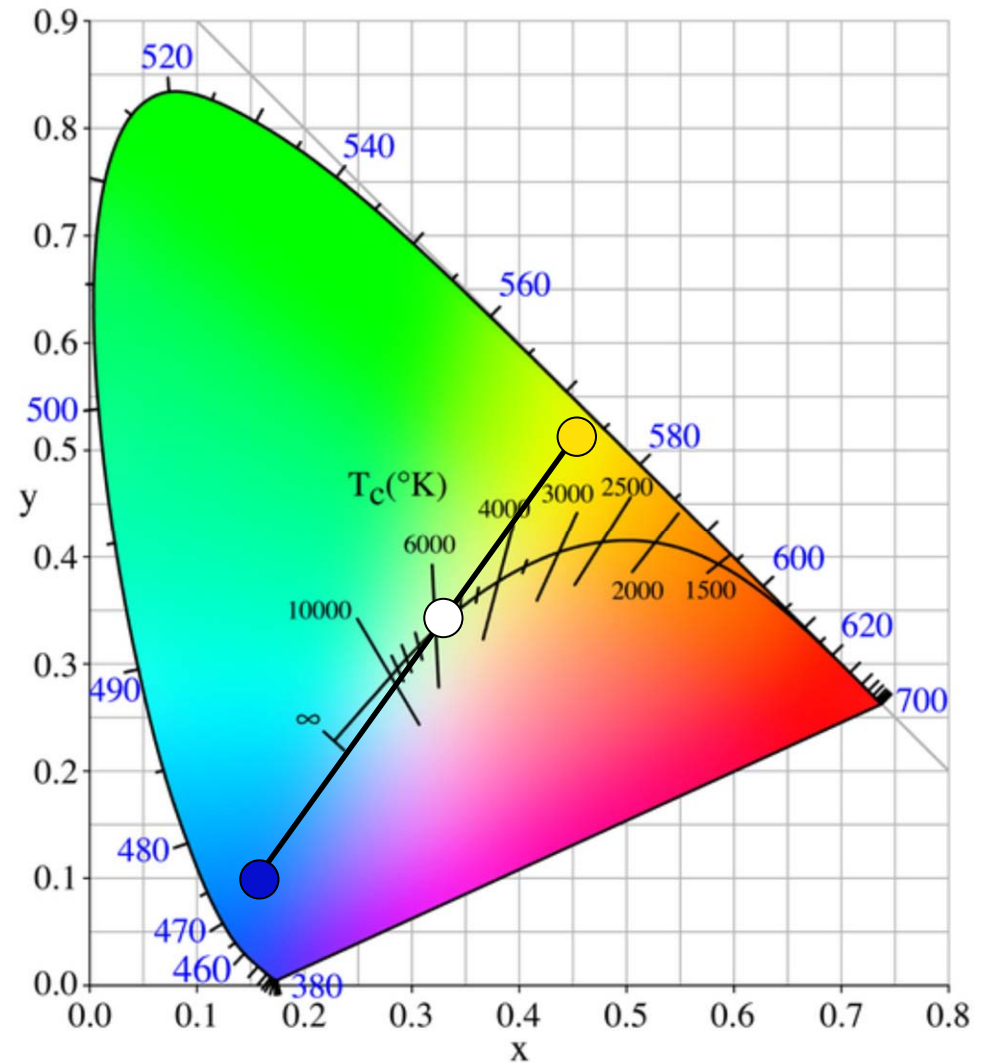


Desired characteristics

- ◆ luminous efficiency > 160 lumens/W
- ◆ System efficiency > 50%
- ◆ Color coordinates on the Planckian locus with color temperature between 3000K and 6000K
- ◆ CRI > 85
- ◆ Lifetime > 50,000 h
- ◆ Lifecycle cost less than a few \$/million lumen-hours

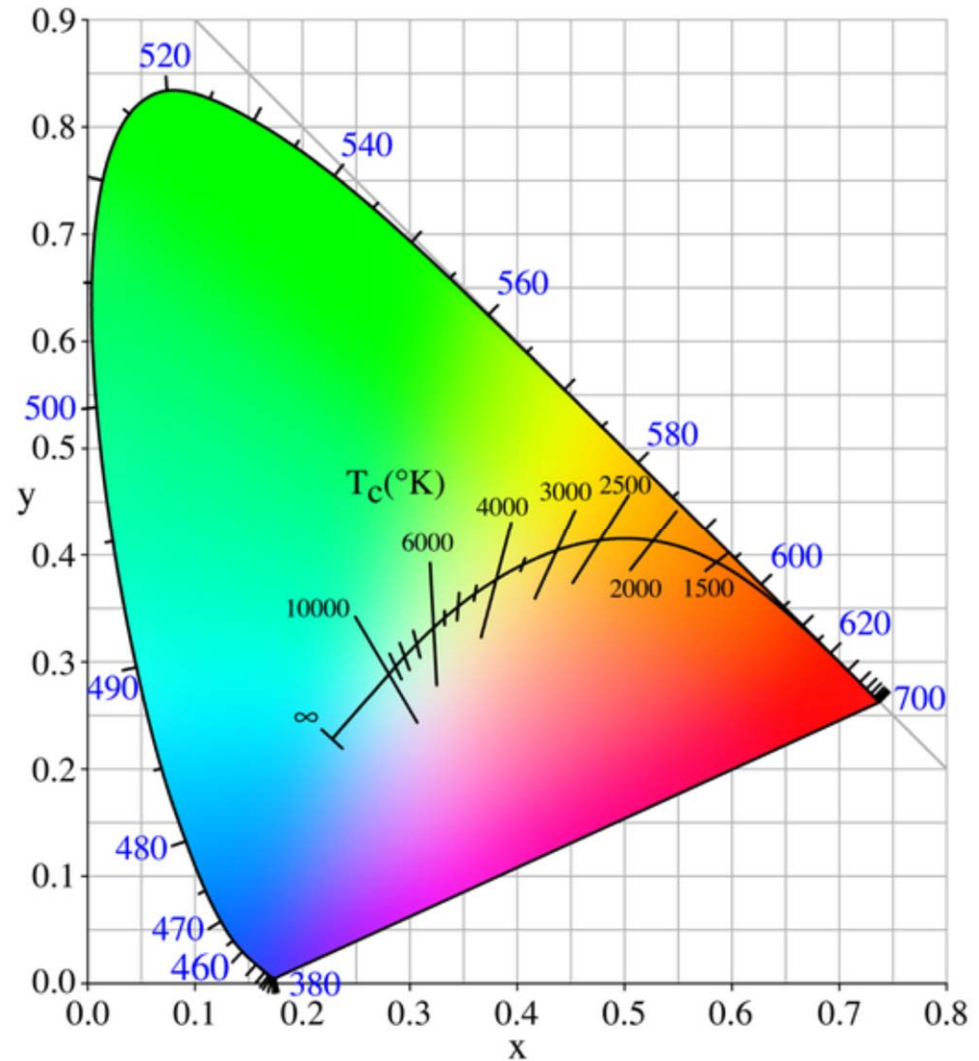

Light-Emitting Diodes (LEDs)

- ◆ Semiconductor p-n junction under forward bias
- ◆ Injected holes, electrons or both annihilate to generate a photon (radiative recombination)
- ◆ Wavelength determined by bandgap of the active region
- ◆ Monochromatic - ideal for traffic lights and safety signage

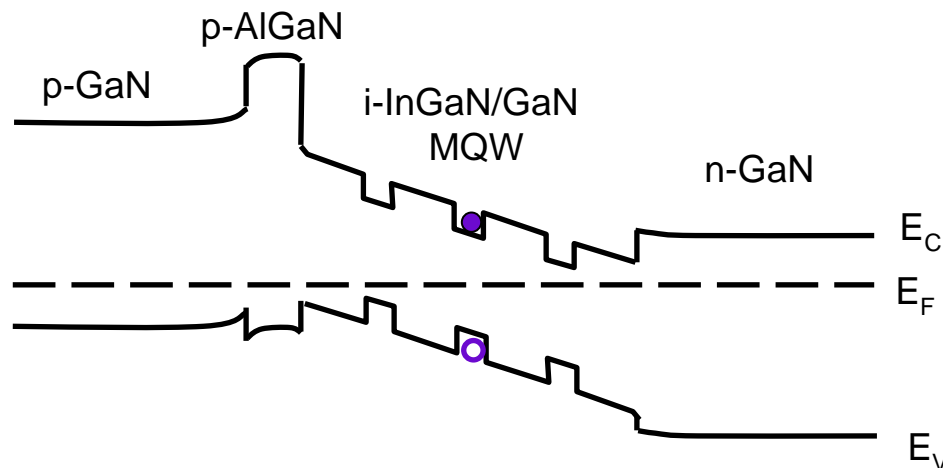

Typical band diagram at zero bias for a visible nitride LED

LED efficiency

$$\eta_{\text{wall-plug}} = \eta_{\text{feeding}} \cdot \eta_{\text{injection}} \cdot \underbrace{\eta_{\text{IQE}} \cdot \eta_{\text{optical}}}_{\eta_{\text{EQE}}}$$

Feeding efficiency: mean energy of photon emitted/ qV_f .

Injection efficiency: fraction of electrons passing through diode that are injected into the active region.


Internal quantum efficiency (IQE): fraction of e-h pairs recombining in active region that recombine radiatively.

Optical extraction efficiency: fraction of photons generated that escape from the device.

External quantum efficiency (EQE): number of photons emitted/number of electrons passing through diode


Bandgap vs. lattice constant

- ◆ **Desired:** a vertical black line traversing the visible spectrum

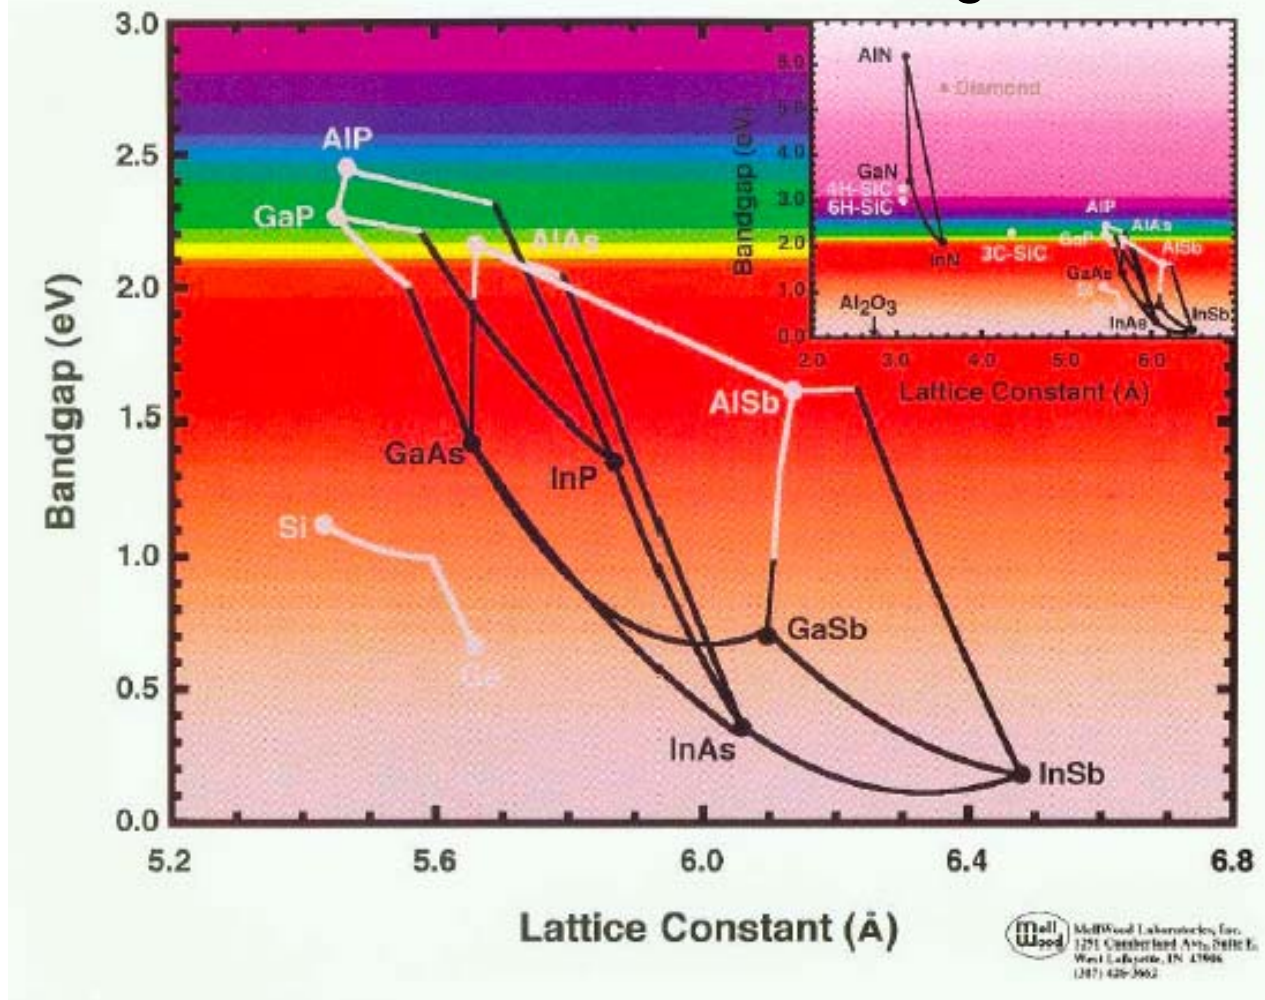


LEDs across the visible

- ◆ III-V LEDs cover the visible spectrum, but not with one materials system

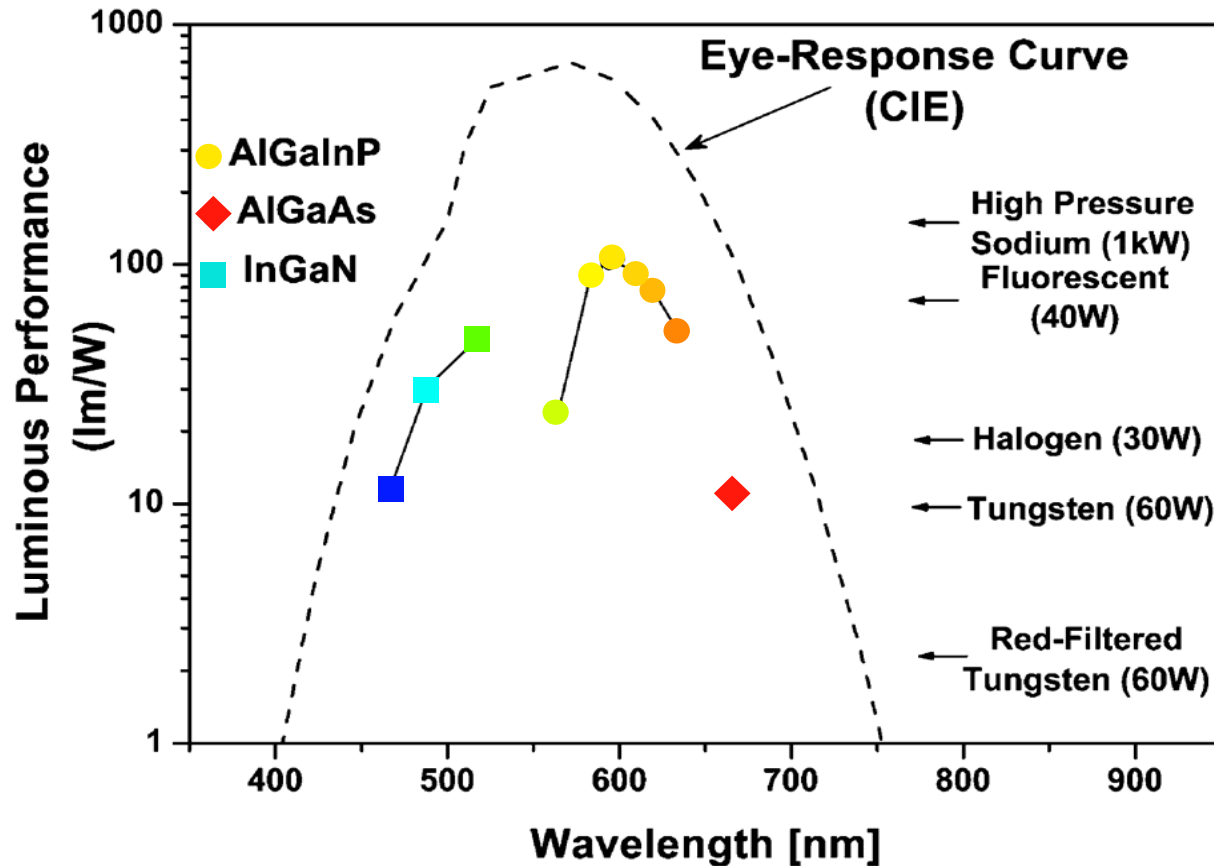

Why not full-spectrum emission from (In,Ga)N?

- ◆ Extended defects resulting from strain/miscibility gap act as nonradiative recombination sites
- ◆ Critical thickness of (In,Ga)N/GaN limited to a few nm for compositions that emit in the visible
- ◆ (In,Ga)N quantum well/quantum dot LEDs efficient in blue and green only

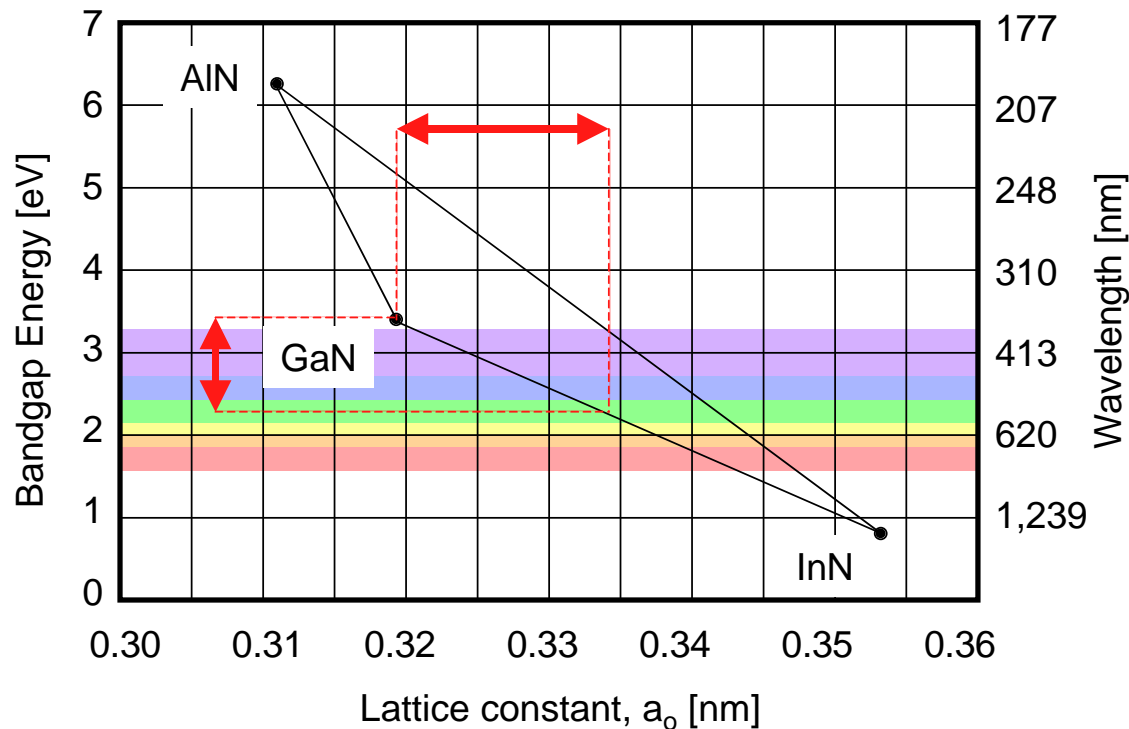

Efficiency trends

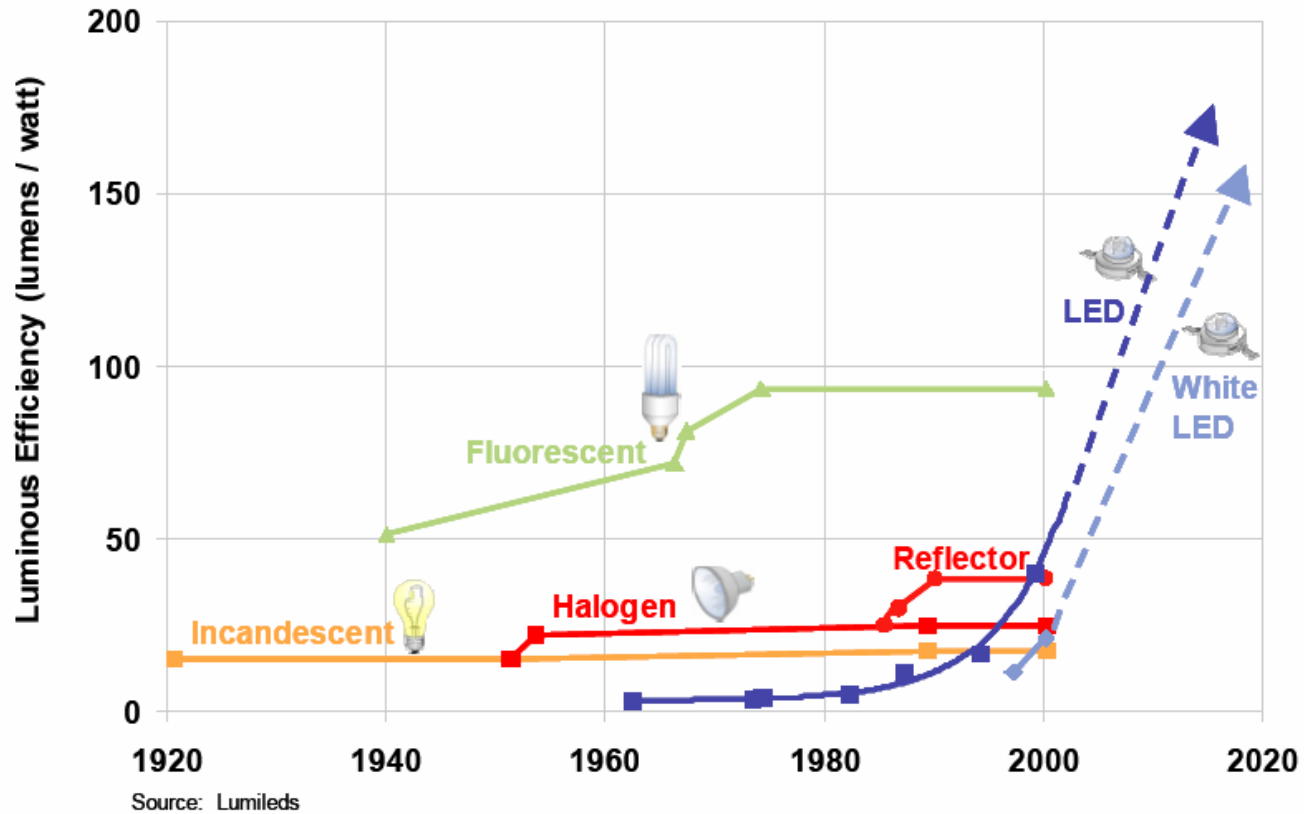


Figure 2-1: Historical and Predicted Efficacy of Light Sources

Source: Lumileds.

“Solid-State Lighting Research and Development Portfolio - Multi-Year Program Plan FY’07-FY’12,
 “prepared for DoE by Navigant Consulting, March 2006

Performance comparison (2005)

Table 2-1: Typical Performance of LED Devices and Conventional Technologies


Color	Luminous Output	Wattage	Luminous Efficacy	CCT (Typical)/ Dominant Wavelength	CRI	Lifetime
White	45 lm	1W	45 lm/W	5500°K	70	50k hours
Warm White	20 lm	1W	20 lm/W	3300°K	90	50k hours
Green	53 lm	1W	53 lm/W	530 nm	N/A	50k hours
Blue	16 lm	1W	16 lm/W	470 nm	N/A	50k hours
Red	42 lm	1W	42 lm/W	625 nm	N/A	50k hours
Amber	42 lm	1W	42 lm/W	590 nm	N/A	50k hours
Incandescent	850 lm	60W	14 lm/W	3300°K	100	1k hours
Fluorescent	5300 lm	32W	83 lm/W	4100°K	78	20k hours
HID	24,000 lm	400W	80 lm/W	4000°K	65	24k hours

Notes: For LED devices - drive current = 350ma, 1W device, $T_j=25^\circ\text{C}$, batwing distribution, lifetime measured at 70% lumen maintenance. Lumen output is measure in mean lumens.

Source: Lumileds, 2005. GE, 2005. Philips Lighting, 2005. OSRAM Sylvania, 2005. Product Catalogs.

“Solid-State Lighting Research and Development Portfolio - Multi-Year Program Plan FY’07-FY’12,
 “prepared for DoE by Navigant Consulting, March 2006

Haitz's Law

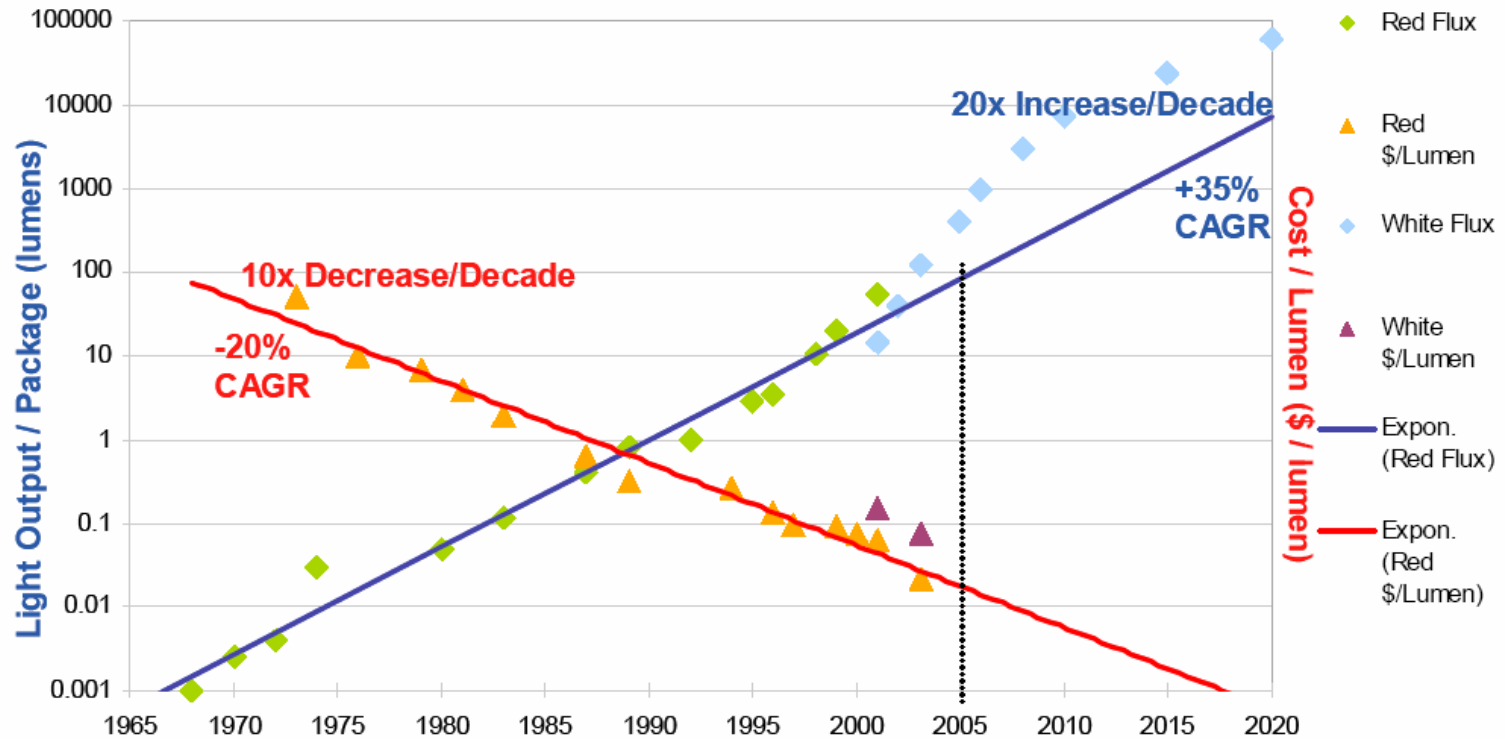

Source: Roland Haitz & Lumileds

Figure 2-4: Haitz's Law: LED Light Output Increasing / Cost Decreasing

Source: Roland Haitz and Lumileds.

Note: CAGR = compound annual growth rate. Both lines are on the same numerical scale (however, different units)

"Solid-State Lighting Research and Development Portfolio - Multi-Year Program Plan FY'07-FY'12," prepared for DoE by Navigant Consulting, March 2006

True cost of light

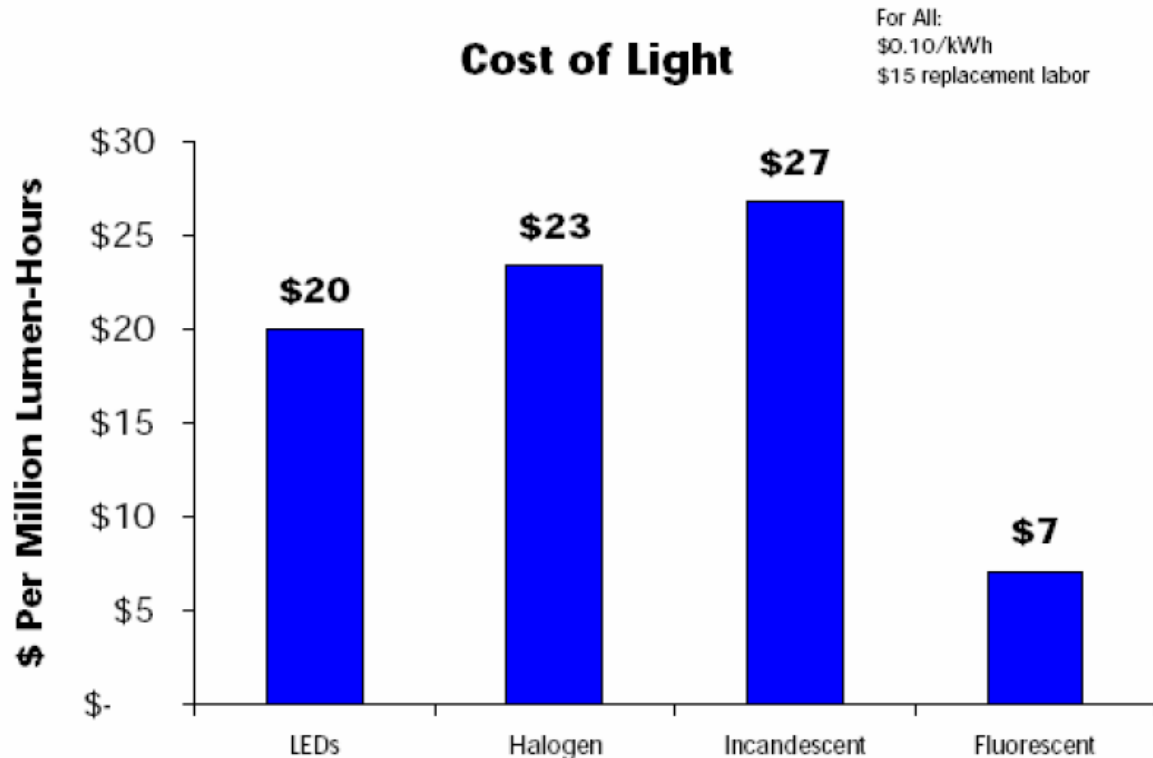



Figure 2-5: Cost of Light

Note/Source: To see how these values were calculated, please see the complete paper: “Cost of Light – When does Solid-state Lighting make Cents?” by Kevin Dowling, Color Kinetics, September 12, 2003.


“Solid-State Lighting Research and Development Portfolio - Multi-Year Program Plan FY’07-FY’12, “prepared for DoE by Navigant Consulting, March 2006

SSL approaches: *blue GaN LED + phosphor*

- ◆ blue GaN LED with yellow phosphor embedded in epoxy dome

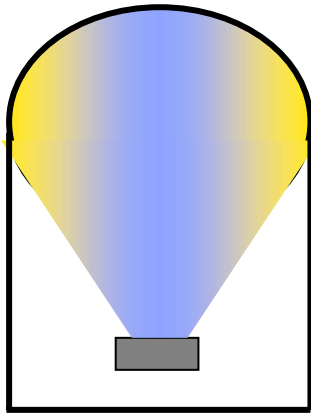


- ◆ *Low cost, but poor Color Rendering Index (CRI)*

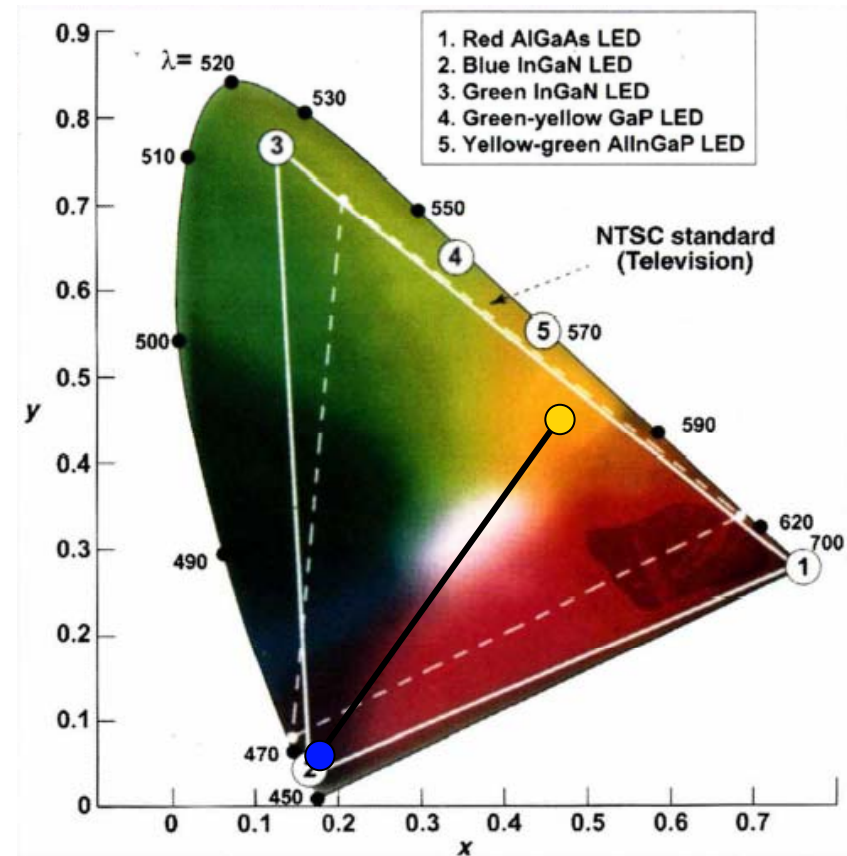


Chromaticity Diagram (CIE 1931)
Nitride-based Semiconductors for Blue and Green Light-emitting devices, FA Ponce and DP Bour, Nature 386 (1997) 351-9

SSL approaches: *uv GaN LED + phosphors*

- ◆ uv GaN LED with multiple phosphors embedded in epoxy dome

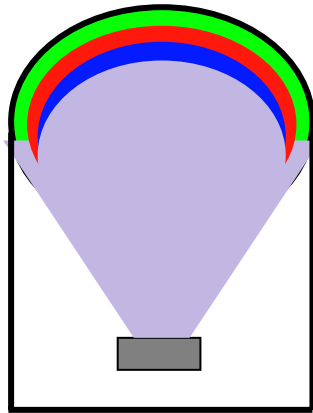


- ◆ *High CRI, but inefficient red phosphor, down-conversion losses and lamp lifetime concerns*

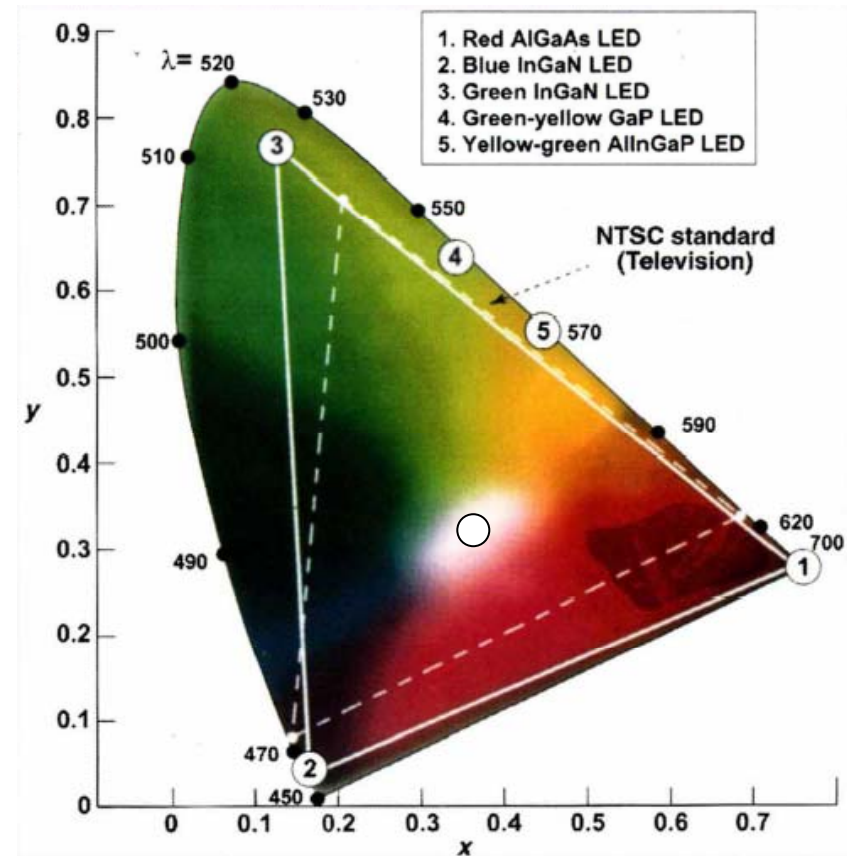


Nitride-based Semiconductors for Blue and Green Light-emitting devices, FA Ponce and DP Bour, Nature 386 (1997) 351-9

SSL approaches: *multichip*

- Integration of (Al,Ga,In)N (blue and green) with (Al,Ga,In)(As,P) (red) at the breadboard level

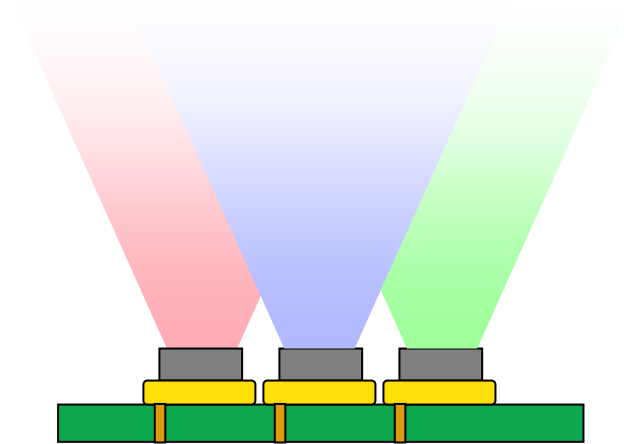


- Great for large area displays...too expensive for general illumination!

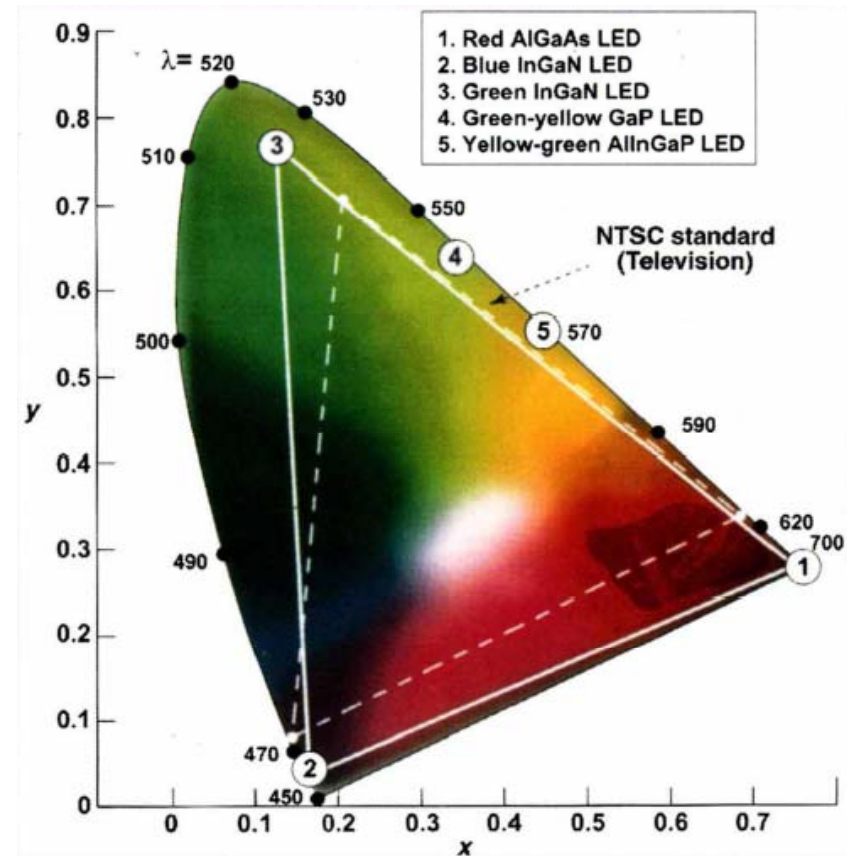


Nitride-based Semiconductors for Blue and Green Light-emitting devices, FA Ponce and DP Bour, Nature 386 (1997) 351-9


SSL approaches: *microdie transfer*

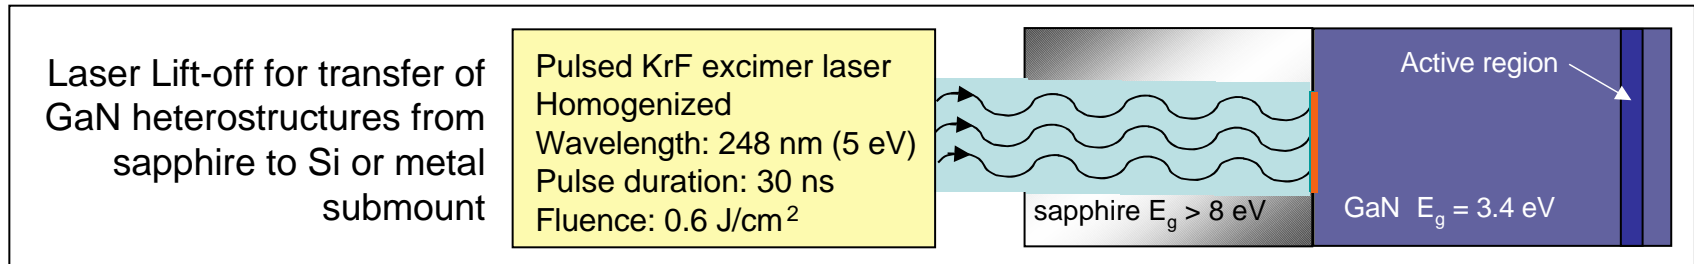

- ◆ Integration at the wafer level by microdie transfer

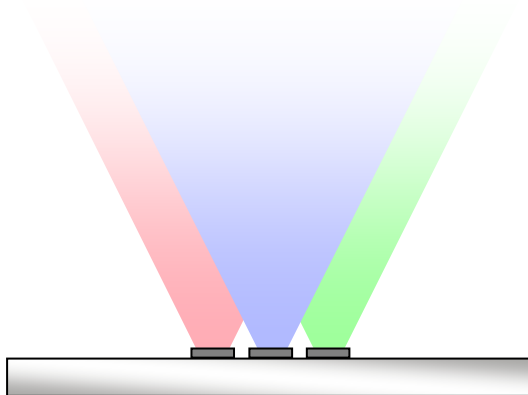

- ◆ *Potentially lower cost than multichip approach, but may be too complex and expensive for general illumination*

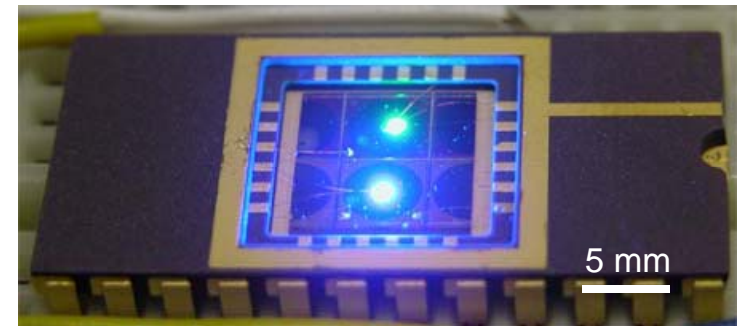


Dual wavelength Fluorescence Detection Microsystem with blue and green microdie LEDs transferred to Si by laser lift-off

Z. Luo, J.A. Chediak, J. Seo, N. Cheung, L.P. Lee and T.D. Sands, presented at the 2003 Electronic Materials Conference, Salt Lake City, June 25th, 2003

SSL approaches: *heteroepitaxy*


- ◆ Selective-area heteroepitaxy of (Al,Ga,In)N on (Al,Ga,In)(As,P) or vice versa

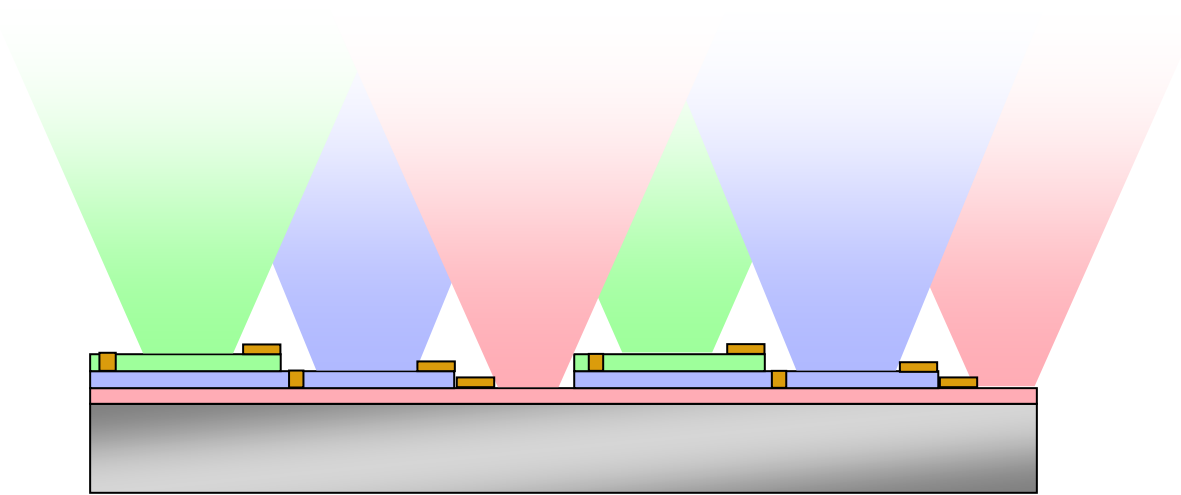

- ◆ *Eliminates layer transfer and bonding*
- ◆ *Creates problems associated with...*
 - ◆ *Incompatible growth and processing conditions*
 - ◆ *Defects due to symmetry, lattice, and CTE mismatch*
 - ◆ *Nonplanar surface*
 - ◆ *Multilevel metallization*

SSL approaches: *OLEDs*

- ◆ Organic Light-Emitting Diodes

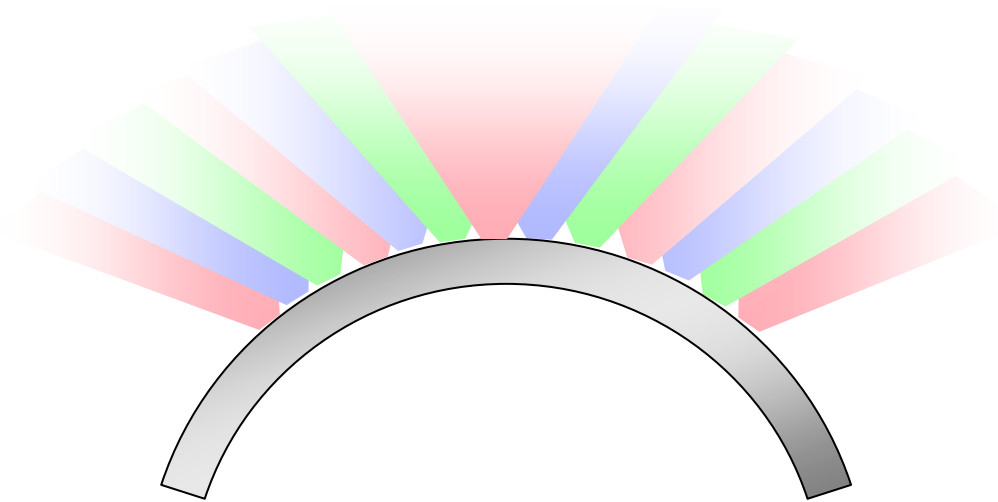

- ◆ *Potentially low cost - fabricated by spin coating, thermal evaporation or ink jet printing*
- ◆ *Flexible - multiple colors on the same substrate*
- ◆ *Issues: efficiency (white), color uniformity, lamp lifetime, need for hermetic sealing*
- ◆ *Great for flexible displays - lifetime issue may preclude illumination applications*



SSL approaches: *ideal?*

*monolithic, phosphor-free white LED from
one materials system*

...(In,Ga)N??

Opportunities - *Nano*

- ◆ Nanoheteroepitaxy for strain-engineered phosphor-free white LEDs based on (In,Ga)N
- ◆ Photonic crystals and nanoplasmonics for enhanced coupling of light out of the semiconductor

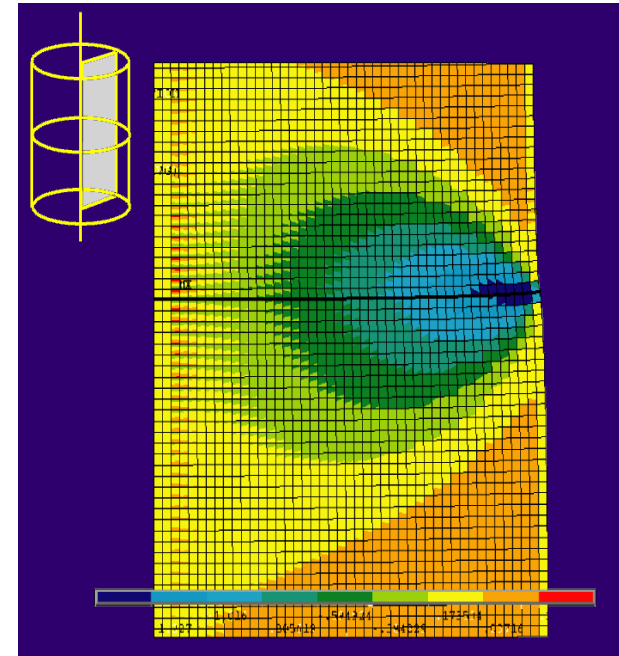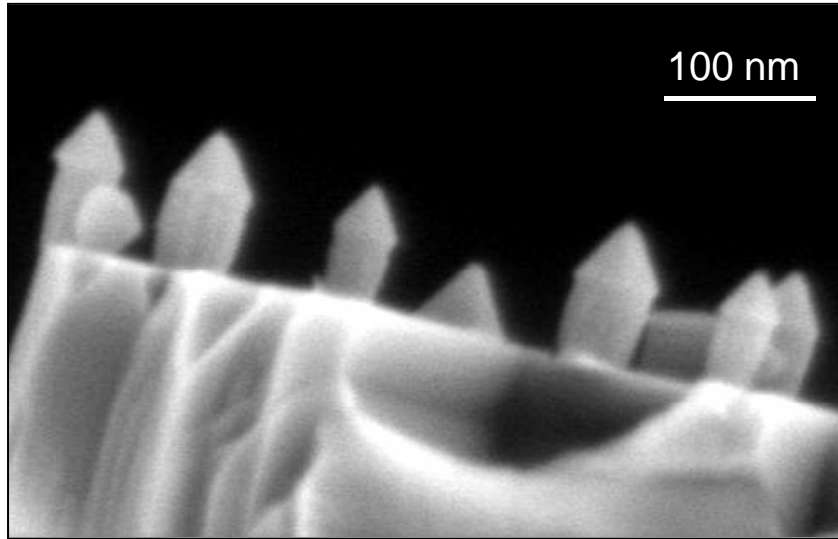

Recommended Reading

- ◆ “Physics of Semiconductor Devices,” Sze (Wiley, NY, 1981)
- ◆ “Introduction to Solid State Lighting,” Zukauskas, Shur and Gaska (Wiley, NY, 2002)
- ◆ <http://www.netl.doe.gov/ssl/>

tsands@purdue.edu

Questions & Answers